# SHANGHAI JIAO TONG UNIVERSITY LECTURE 4 2017

# **Anthony J. Leggett**

Department of Physics University of Illinois at Urbana-Champaign, USA and Director, Center for Complex Physics Shanghai Jiao Tong University

1

# <u>Ginzburg – Landau (GL) theory of superconductivity</u>

Formulated 1950 (pre – BCS): even in 2017 mostly adequate for "engineering" applications of superconductivity. (SC)

historically, takes its origins in general Landau-Lifshitz theory (1936) of 2<sup>nd</sup> order phase transitions, hence quantitative validity confined to T close to  $T_c$ . Here, I will start by arguing "with hindsight" for its qualitative validity at T = 0, and only later generalize to  $T \neq 0$  and in particular  $T \rightarrow T_c$ .

Recall: could explain 3 major characteristics of SC state (persistent currents, Meissner effect, vanishing Peltier coefficient) by scenario in which fermionic pairs form effective bosons, and these undergo BEC. Suppose that N fermions form N/2 bosons, which are then condensed into the same 2 – particle state, Neglect for now relative wave function and df.

> COM wave function of condensed pairs  $\equiv \varphi(\mathbf{r})$  **1** COM coordinate

What is energy  $E_o$  (at T = 0) of pairs as function(al) of  $\varphi(\mathbf{r})$ ?

At first sight, for a single pair,

$$E_o\{\varphi(\mathbf{r})\} = -E_b \int |\varphi(\mathbf{r})|^2 d\mathbf{r} + \frac{\hbar^2}{2m} \int \left| \left( \nabla - \frac{2ie}{\hbar} A(\mathbf{r}) \right) \varphi(\mathbf{r}) \right|^2$$

binding energy of pair

2 electrons involved!

so, convenient to define

——— "order parameter" (OP)

$$\Psi(\mathbf{r}) \equiv \sqrt{\frac{N}{2}}\varphi(\mathbf{r})$$

$$\alpha_{T=0} \equiv E_b$$

then energy of N/2 pairs is

$$E_o\{\Psi(\boldsymbol{r})\} = \text{const.} + \int d\boldsymbol{r} \left\{ -\alpha_{T=0} |\Psi(\boldsymbol{r})|^2 + \frac{\hbar^2}{2m} \left| \left( \nabla - \frac{2ie}{\hbar} \boldsymbol{A}(\boldsymbol{r}) \right) \Psi(\boldsymbol{r}) \right|^2 \right\}$$

However, by itself this will not generate stability of supercurrents (lecture 3). To do so, must add (*e.g.*) term in  $|\Psi|^4$ ... Adding also EM field term:

$$E_{0}\{\Psi(\boldsymbol{r})\} = \int dr \begin{cases} -\alpha_{T=0}|\Psi(r)|^{2} + \frac{1}{2}\beta_{T=0}|\Psi(r)|^{4} + \frac{\hbar^{2}}{2m}\left|\left(\nabla - \frac{2ie}{\hbar}\boldsymbol{A}(\boldsymbol{r})\right)\Psi(r)\right|^{2} \\ + \frac{1}{2}\mu_{0}^{-1}(\nabla \times \boldsymbol{A}(\boldsymbol{r}))^{2} \end{cases}$$

$$(Standard'' form of GL (free))$$

$$(at T=0)$$

Notes:

1. Normalization of  $\Psi(r)$  is conventional and arbitrary. Rescaling

$$\Psi^{1}(r) \equiv q\Psi(r), \alpha'_{T=0} \equiv q^{-2}\alpha_{T=0}, \beta'_{T=0} \equiv q^{-4}\beta_{T=0}, \hbar^{2}/2m \to \hbar^{2}/2mq^{2}$$

leaves E<sub>0</sub> unchanged.

2. If 
$$A(\mathbf{r}) = 0$$
 and  $\Psi(r) = \text{constant} \equiv \Psi_{T=0}^{eq}$ , then value is

$$\Psi_{T=0}^{eq} = (\alpha_{T=0}/\beta_{T=0})^{1/2}$$

and energy is  $E_{T=0}^{eq} = -\alpha_{T=0}^2/2\beta_{T=0}$ 

3. Minimization with respect to  $A(r)(\delta E_o/\delta A(r) = 0)$  yields Maxwell's equation  $\nabla \times H = \mathbf{j}(\mathbf{r})$ 

provided that we identify

$$j(\mathbf{r}) = \frac{e}{m} (\Psi^*(r)(-i\hbar \nabla - 2e\mathbf{A})\Psi(r) + c.c.)$$

4. Minimization with respect to  $\Psi(\mathbf{r})(\delta E_0/\delta \Psi(\mathbf{r}) = 0)$  yields

$$-\alpha_{\rm T=0}\Psi(r) + \beta_{\rm T=0}|\Psi(r)|^2\Psi(r) - \frac{\hbar^2}{2m} \left(\nabla - 2\frac{ie}{\hbar}A(r)\right)^2\Psi(r) = 0$$

Note that for A(r) = 0 this defines a characteristic length

$$\xi_{\mathrm{T}=0} \equiv \left(\frac{\hbar^2}{2m\alpha_{\mathrm{T}=0}}\right)^{1/2}$$

A second characteristic length follows if we put  $\Psi(r) = \text{constant} \equiv \Psi_0$ and compare terms in  $A^2$  and  $(\nabla \times A)^2$ .

$$\lambda_{\rm T=0} \equiv (2m/e^2\mu_0|\Psi_0|^2)^{-1/2}$$

or since with our normalization  $\Psi_0 = \sqrt{N/2V}$  ,

 $\lambda_{\mathrm{T}=0}\equiv (m/\mu_0 e^2 n)^{-1/2}~~(\equiv$  London penetration depth at T = 0)

electron density

Generalization to  $T \neq 0$ :


All we need do is to let  $E_0 \rightarrow F(T)$  and let the coefficients  $\alpha_0$ ,  $\beta_0$  be T – dependent:

$$F(\Psi(r):T) = F_0(T) + \int dr \mathcal{F}(r,T)$$

$$\mathcal{F}(r, \mathbf{T}) \equiv -\alpha(\mathbf{T})|\Psi(r)|^{2} + \frac{1}{2}\beta(\mathbf{T})|\Psi(r)|^{4} + \frac{\hbar^{2}}{2m} \left| \left( \boldsymbol{\nabla} - \frac{2ie}{\hbar} \mathbf{A}(r) \right) \Psi(r) \right|^{2} + \mu_{0}^{-1} \left( \boldsymbol{\nabla} \times \mathbf{A}(r) \right)^{2}$$

## standard form of GL free energy density


Note that there is now a contribution to  $\alpha(T)$  (and possibly also  $\beta(T)$ ) from the entropy term  $-TS\{\Psi(r)\}$ . (condensate itself carries no entropy, but electrons "liberated" from it do!)

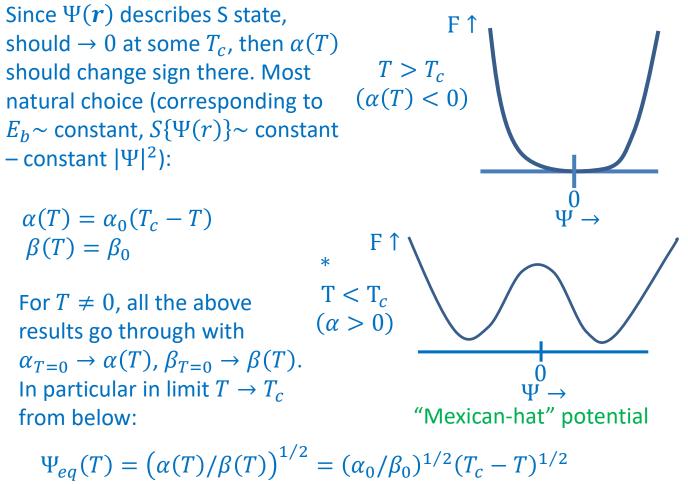

$$\begin{split} F_{eq}(T) - F_0(T) &= -\alpha^2(T)/2\beta(T) = -(\alpha_0^2/2\beta_0)(T_c - T)^2\\ \xi(T) \propto [\alpha(T)]^{-1/2} \propto (T_c - T)^{-1/2}\\ \lambda(T) \propto \left[\Psi_{eq} \cdot (T)\right]^{-1} \propto (T_c - T)^{-1/2} \end{split}$$

so ratio  $\kappa \equiv \lambda/\xi$  is independent of T in limit  $T \to T_c$ . From  $F_{eq}(T) - F_0(T) \propto (T_c - T)^2$ , entropy S has no discontinuity at  $T_c$ ,


but sp. ht.  $C_v \equiv T dS/dT$ has discontinuity  $T_c \alpha_0^2 / \beta_0 \Rightarrow$  second order phase transition at  $T_c$ .

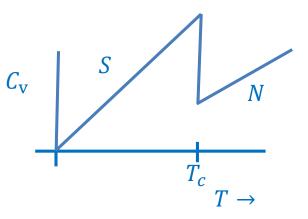

#### Some simple applications of the GL theory

A. Zero magnetic field (A = 0)

1. <u>Recovery of OP near wall (etc.)</u> Suppose boundary condition at z = 0 is that  $\Psi$  must  $\rightarrow 0$  (*e.g.* wall ferromagnetic). Then must solve GL eq

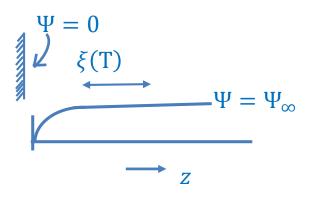

$$\alpha(T)\Psi(z) + \beta_0 |\Psi(z)|^2 \Psi(z) - \frac{\hbar^2}{2m} \frac{\partial^2 \Psi(z)}{\partial 2^2} = 0$$

subject to boundary conditions

 $\Psi(z=0)=0$ 

$$\Psi(z \to \infty) = \Psi_{\infty} \equiv (\alpha (T) / \beta_0)^{1/2}$$

Solution:

 $\Psi(z) = \Psi_{\infty} \tanh(z/2\xi(T))$ 

$$\xi(T) \equiv (\hbar^2/2m\alpha(T))^{-1/2} \propto (T_c - T)^{-1/2}$$

Note:  $\Psi$  does **not** have to vanish at boundary with vacuum or insulator! [except on scale  $\sim k_F^{-1}$  where N state wave functions do too] Thus, no objection to SC occurring in grains of dimension  $\ll \xi(T)$ . However, contact with N metal tends to suppress SC.

#### 2. Current – carrying state in thin wire

If  $d \ll \lambda(T)$ , can neglect **A** to first approximation d

By symmetry,

 $\Psi = |\Psi| \exp i\varphi, |\Psi| = \text{constant}, \mathbf{j} = \frac{2e\hbar}{m} |\Psi|^2 \nabla \varphi$ 

 $F = -\alpha(\mathbf{T})|\Psi|^{2} + \frac{\beta_{0}}{2}|\Psi|^{4} + \frac{\hbar^{2}}{2m}|\Psi|^{2}(\nabla\varphi)^{2} \qquad \text{velocity''} \\ \left(\mathbf{v}_{s} = \frac{\hbar}{2m}\nabla\varphi\right)$ 

and we need to minimize this with respect to  $|\Psi|$  for fixed  $\nabla \varphi$ . Result:


$$|\Psi| = \left(\frac{\alpha(T) - \frac{\hbar^2}{2m} |\nabla\varphi|^2}{\beta_0}\right)^{1/2} \equiv \Psi_{\infty}(1 - \xi^2(T))(\nabla\varphi)^2)^{1/2}$$

⇒  $|\Psi| \rightarrow 0$  for  $\nabla \varphi = \xi^{-1}(T)$  (condensation energy changes sign). However, *j* is **nonmonotonic** function of  $\nabla \varphi$ , with maximum at point when  $\nabla \varphi = \frac{1}{\sqrt{3}}\xi^{-1}(T)$ . (at which point  $|\Psi| = \sqrt{2/3} \Psi_{\infty}$ ). Thus, critical current *j<sub>c</sub>* given by

$$j_c = \frac{2e\hbar}{m} \cdot \frac{2}{3} \frac{\alpha(T)}{\beta_0} \frac{1}{\sqrt{3}} \xi^{-1}(T) \propto \alpha^{-1}(T) \xi^{-1}(T) \propto (1 - T/T_c)^{3/2}$$

#### **B.** Behavior in magnetic field

Because of the Meissner effect, any superconductor will completely expel a weak magnetic field. If we consider just the competition between the resulting state and the *N* state, we have (per unit volume)

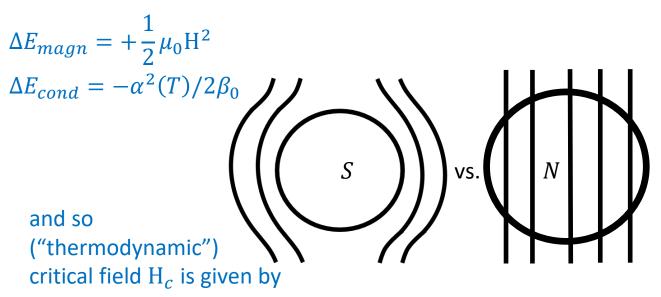


 $H_c(T) = (\alpha^2(T)/\mu_0\beta_0)^{1/2} \propto (1 - T/T_c)$ 

However, in general this works only for "type-I" superconductors in form of long cylinder parallel to field. More generally:

- (a) in type-I superconductors, "intermediate" state forms with interleaved macroscopic regions of *N* and *S*.
- (b) in type-II superconductors, magnetic field "punches through" sample in the form of vortex lines.

#### Isolated vortex line

Consider  $\lambda(T) \gg \xi(T)$ ("extreme type-II")

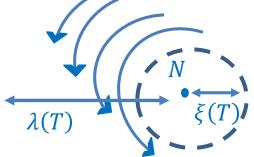

Magnetic field turns region  $\sim \xi^2(T)$  normal, and "punches through" there. Field is screened out of bulk on scale  $\lambda(T) \gg \xi(T)$ 


At distances  $\gg \lambda(T)$ , no current flows: however since  $\mathbf{j} \propto \nabla \varphi - \frac{2e}{\hbar} \mathbf{A}$ 

 $\nabla \varphi$  and A may be individually non zero, with  $\nabla \varphi = \frac{2e}{\hbar}A$ . But  $\varphi$  must be single-valued mod.  $2\pi$ , hence

$$\oint \nabla \varphi \cdot d\ell = 2n\pi \Longrightarrow \oint A \cdot d\ell \equiv \Phi = n\Phi_0$$
trapped flux
$$h/2e$$

"superconducting" flux quantum

n = 0 is trivial (no vortex!) and  $|n| \ge 2$  is unstable, so restrict consideration to  $n = (\pm)1$ . Since field extends over  $\sim \lambda(T)$  into bulk metal, field at core  $(\equiv H_0) \sim \Phi_0 / \lambda^2(T)$ .

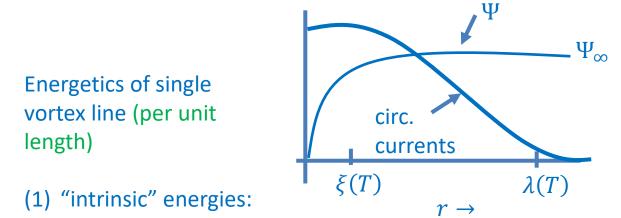

- (a) field energy  $\sim \frac{1}{2} \mu_0 H_0^2 \lambda^2 \sim \varphi_0^2 / (\mu_o \lambda^2)$
- (b) (minus) condensation energy  $\sim -\frac{1}{2}\mu_0 H_c^2 \xi^2$
- (c) flow energy:  $v_s \sim \frac{\hbar}{2m} \frac{1}{r}$ , for  $r \leq \lambda(T)$ , so

$$(c) \sim |\Psi_{\infty}|^{2} \left(\frac{\hbar}{2m}\right)^{2} \int_{\xi}^{\lambda} \frac{rdr}{r^{2}} \sim |\Psi_{\infty}|^{2} \frac{\hbar^{2}}{(2m)^{2}} \ell n(\lambda/\xi)$$

but  $\lambda(T) = (\mu_0 |\Psi_{\infty}|^2 e^2 / m)^{-1/2}$ , so  $(c) \sim (\Phi_0^2 / \mu_0 \lambda^2(T)) \ell n(\lambda/\xi)$ 

> dominant over (a) and (b) for  $\lambda(T) \gg \xi(T)$

Thus "intrinsic" energy per unit length of vortex lines for  $\lambda \ll \xi$  is  $E_0(T) \sim \left( \Phi_0^2 / (\mu_o \lambda^2(T)) \cdot \ell n(\lambda/\xi) \right).$  (2) On the other hand, the "extrinsic" energy saving due to admission of the external field is  $\sim \mu_0 H_{ext} H_0 \sim H_{ext} (\Phi_0 / \lambda^2)$ . Hence the condition for it to be energetically advantageous to admit a single vortex line is roughly

 $\mathbf{H}_{ext} \sim \left( \Phi_0 / \lambda^2(T) \right) \cdot \ell n \kappa \quad \left( \kappa \equiv \lambda(T) / \xi(T) \neq f(T) \right)$ 

This defines the lower critical field  $H_{c1}$ .

What is the maximum field the superconductor can tolerate before switching to the *N* phase?

Roughly, defined by the point at which the vortex cores (area  $\sim \xi^2(T)$ ) start to overlap. Since for near-complete penetration we must have  $n\Phi_0 \sim H_{ext}$ , this gives the condition

number of vortices/unit area

 $\mathbf{H}_{ext} \sim \left( \Phi_0 / \xi^2(\mathbf{T}) \right)$ 

This defines the upper critical field  $H_{c2}$ 

Note that for  $\lambda(T) \leq \xi(T)$ , we have  $H_{c1} \gtrsim H_{c2}$  and would expect type-I behavior.

Results of more quantitative treatment:

(a) condition for type-II behavior is  $\kappa \equiv (\lambda(T)/\xi(T)) > 2^{-1/2}$ 

(b) in extreme type-II limit  $\kappa \gg 1$ ,

$$\mathbf{H}_{c1}(T) = \left(\Phi_0 / 4\pi\lambda^2(\mathbf{T})\right) \ell n\kappa$$

(c) in same limit,

 $\mathrm{H}_{c2}(T) = \Phi_0 / 2\pi \xi^2(\mathrm{T}).$ 

Note that quite generally we have up to logarithmic factors

$$H_{c1}(T) \cdot H_{c2}(T) \sim H_c^2(T)$$
  
thermodynamic  
critical field

hence if  $H_c(T)$  held fixed,  $H_{c1}$  varies inversely to  $H_{c2}$ 

#### Application: dirty superconductors

Alloying does not change  $E_{cond}(T)$ , hence  $H_c^2(T)$ , much. However, it drastically increases  $\lambda(T)$  ( $\xi(T)$  is also increased, but less). Hence  $\kappa$  is increased, and many elements which on type-I when pure became type-II when alloyed. As alloying increases,  $H_{c2}$  increases while  $H_{c1}$ decreases.

## Summary of lecture 4

Ginzburg-Landau theory is special case of Landau-Lifshitz theory of 2<sup>nd</sup> order phase transitions: quantitatively valid only near  $T_c$ . Introduces order parameter ("macroscopic wave function") $\Psi(r)$  which couples to vector potential A(r) with charge 2e:

 $F\{\Psi(r)\} = \text{const.} -\alpha |\Psi(r)|^2 + \frac{1}{2}\beta |\Psi(r)|^4 + \text{const.} \left| \left( \nabla - \frac{2ie}{\hbar} A(r) \right) \Psi(r) \right|^2 + \frac{1}{2}\mu_o^{-1} \left( \nabla \times A(r) \right)^2$ 

2 characteristic lengths:

healing length  $\xi(T)$ 

penetration depth  $\lambda(T)$ 

both  $\propto (T_c - T)^{-1/2}$  for  $T \to T_c$ .

Magnetic behavior depends on ratio  $\kappa = \lambda(T)/\xi(T)|_{T \to T_c}$ 

For  $\kappa > 2^{-1/2}$ , ("type-I") field completely expelled up to a thermodynamic critical field  $H_c(T)$ , at which point turns fully normal.

For  $\kappa < 2^{-1/2}$ , ("type-II") field starts to penetrate at  $H_c$  in form of vortices, continues to do so up to  $H_{c2}$  where turns completely normal.